

STUDY OF PROPERTIES OF WELDED JOINT USING DANTEC'S ISTR A 4D SYSTEMS*

T. DOMAŃSKI, W. PIEKARSKA, M. KUBIAK

Czestochowa University of Technology, Generala I. N. Dabrowskiego 69, 42-201, Czestochowa, Poland

E-mail: domanski@imipkm.pcz.pl

The paper presents displacement and strain fields measured at various stages of tension of flat samples in order to compare the effect of different technological parameters on mechanical properties of welded joints. Results of measurements are also compared with the results of tensile test of the base material to determine the impact of welding process on changes of mechanical properties of tested steel. The measurement of displacements and strains in tensed flat specimens made of S355 steel, hybrid welded using electric arc and laser beam is in the scope of this work. Welding process is performed using Yb:YAG laser and electric arc in GMAW method. D70 Trumpf laser head with maximum power up to 12 kW is used in welding tests with a spot diameter of the laser beam $d=0.8$ mm. Welded joints are made for different technological parameters of the process with laser beam heat source leading in the tandem. Tension tests of flat samples are performed in accordance with norm PN-EN ISO 6892-1. Dantec Q-400 ISTR A multi-camera 3D correlation system is used for strain and displacement measurements. The method of measurement is based on the correlation of digital images recorded by the three cameras. Surface of tested samples is covered with a layer of white and black paint. The measurement took place by tracking movements of spots covering the surface of the sample, loaded by longitudinal force. 6 Ref., 4 Fig.

Keywords: hybrid welding, electric arc, laser, welded joints, mechanical properties, tensile tests, deformation fields

Introduction

Today's facilities are characterized by high functional diversity, which, while maintaining high quality of workmanship, is very difficult. Products are increasingly demanding, and consequently products have increasingly complex 3D geometry. Measurement tools should combine the speed of collection of measurement points with high accuracy. The use of a non-invasive measurement method makes it possible to detect defects much faster without the need for specialist preparation of test specimens [1-3].

Coupled thermal, structural and mechanical phenomena occurring in welding process have a direct impact on the quality of welded joint. The material in the weld and adjacent region is heated to various temperatures resulting in a variety of structures that occur in the joint and heat affected zone (HAZ), having different mechanical properties in comparison to base material. Theoretical and experimental analysis of mechanical behaviour of welded joint is still one of the fundamental industrial problems. In the welding process using a laser beam a high welding speeds are obtained with a good quality of welds and a narrow thermal influence zone which is helpful in increasing the quality and mechanical properties of the joint as well as the production efficiency. One of the modern welding technologies is laser-arc hybrid welding, which combines laser beam

welding with classical electric arc welding cooperating in a single process. This method has many advantages in comparison to welding process with electric arc or laser beam heat sources used separately. Advantages of laser-arc hybrid welding process include higher welding stability, higher melting efficiency, easier input of additional material to the welding pool and a lower input power under the same welding penetration.

The investigations about laser-arc hybrid welded steel have been reported widely and applied successfully in a wide range of the industry. These studies include analytical modeling of thermomechanical phenomena occurring in the process and experimental research on plasma formation, liquid material flow through the welding pool, microstructure composition as well as the analysis of welding deformations and mechanical properties of welded joints, performed in both destructive and nondestructive tests. One of usually performed tests on welded joints is the classical tension test. The standard for this type of testing is the norm PN-EN ISO 6892-1. This test allows the determination of basic mechanical properties of welded joints. However, the development in new measurement systems, such as 3D multicamera correlation system allows the analysis of deformations at the surface area of tensed sample in control area determined for cameras used in the experiment. The knowledge about strain distribution in the joint combined with the analysis of the microstructure of welded joint is essential in determining the material properties in separate joint zones, like the weld, HAZ and transition zone.

* On the materials of the VIII International conference «Beam Technologies in Welding and Materials Processing», 11–15 September 2017, Odessa.

Moreover, the results of such studies are an excellent base for verification of developed theoretical models.

Considering above facts, the main objective of this study are experimental studies on strain during tension of samples welded by laser-arc hybrid technology using GMAW method and Yb:YAG laser beam. Dantec Q-400 Istra multi-camera 3D correlation system is used to measure the distribution of strains during performed tests made on the base material and welded joint. Presented results include tension diagrams as well as a comparison of strain fields measured for the entire tension cycle.

Experimental set-up, hybrid welding

Laser beam emitted by D70 Trumpf laser head with maximum power up to 12 kW is used with electric arc in GMAW method (Fig. 1). Laser head is equipped with collimator lens having a focal length $f_c=200$ mm, and a focusing lens with a focal length $f=400$ mm. The diameter of the beam is set by changing the optical fiber supplying the laser beam to the head. Optical fiber is used in the research having a diameter 0.4 mm. For used optical system double magnification is achieved giving laser focus diameter $d=0.8$ mm. Butt welding is performed for sheets

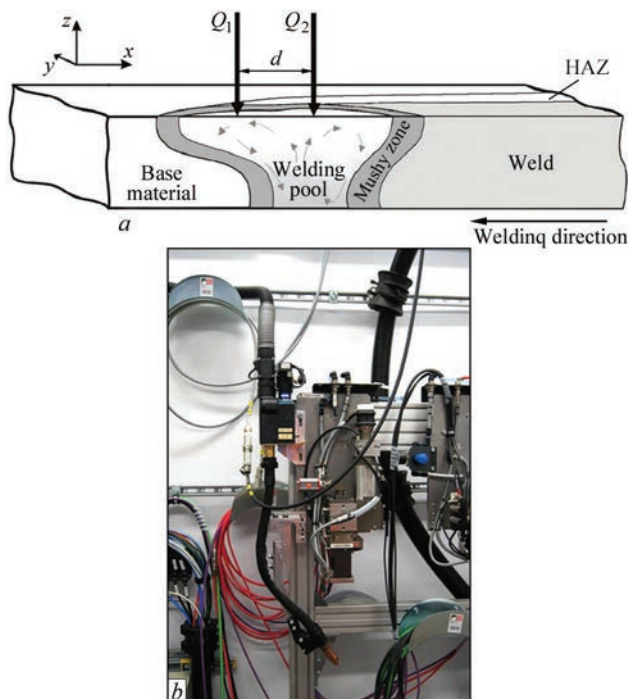


Fig. 1. Scheme of hybrid welding process (a); hybrid laser head Yb: YAG + MIG (b)

made of S355 steel. Welding process proceed without a gap in the shielding gas 82% Ar + 18% CO₂, the gas flow is 18 l/min, wire speed 6m/min and welding speed set to $v=1$ m/min. The distance between heat sources $d=2$ mm. Laser beam is the leading heat source in the tandem.

Samples are welded in the system with leading laser beam in the tandem as well as in inversed system with leading arc. Laser beam power is set to $Q=3$ kW, arc voltage $U=19$ V and current $I=190$ A in the welding experiment.

Strain measurement system

Samples for the tension test were made from welded joints according to norm PN-EN ISO 6892-1. Universal strength machine Zwick&Roel Z100 is used with extensometer Multisens in all performed tension tests. The accuracy of the strength machine is up to 0,1N in force and 1 μ m in displacement. Universal strength machine cooperates with Dantec Q-400 Istra multi-camera 3D correlation system [4-6]. Measurement system is composed of optical cameras used to record strains or deformations. The Timing Box is an interface between the control computer and the sensors for synchronization and analog recording of data, and to power-up cameras and PC computer with a number of network cards, allowing for the introduction of signals from cameras and different sources, transmitted via ethernet and installed dedicated Istra4D software.

In the experiment the system of three cameras was used. Cameras are mounted on the beam which

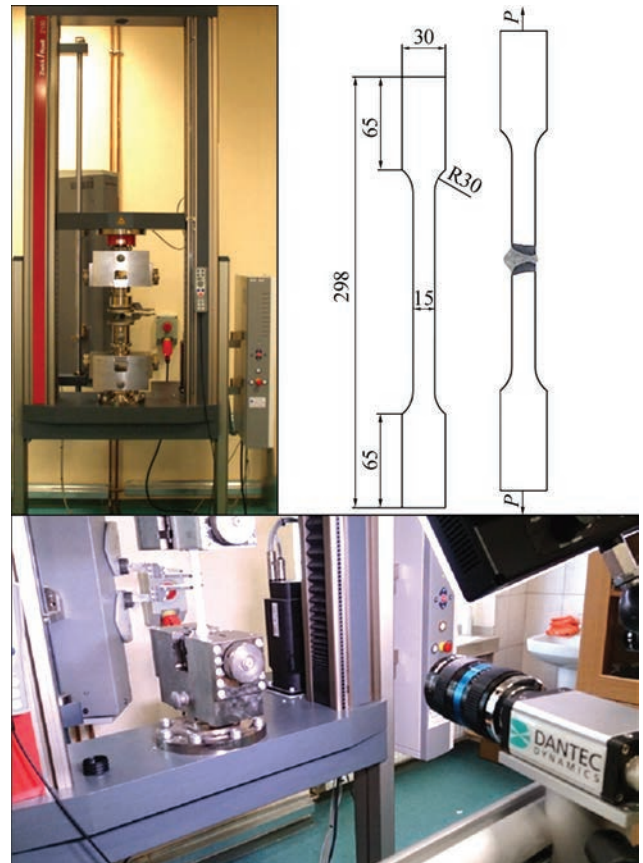


Fig. 2. Tension test: universal strength machine Zwick&Roel Z100, dimension of samples used in the test, Q-400 Istra multi-camera 3D

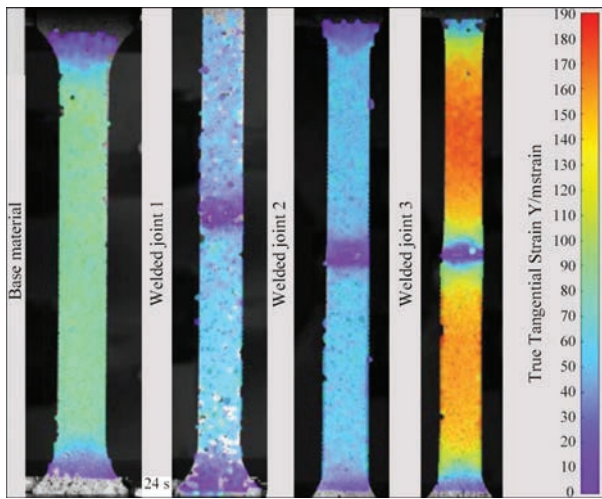


Fig. 3. Strain fields in tensed base material and welded joint ($t=24$ [s])

is supported by two fully adjustable tripods. Optical cameras used to record strains and deformations are equipped with 50 mm, mod: 670 mm lenses and have maximum resolution 4.19 Megapixels, 29 Hz each. This allowed determining the full size of analyzed sample in the working area of universal testing machine. Strain fields are measured for the entire tension cycle. Trigger mechanism is created in Istra4D software for the measurement. Pictures are made for every time increment $\Delta t=0.4$ s.

Results and discussion, strain distributions

Figure 3 presents comparison of strain fields in tensed base material and welded joint at the various measurement steps in elasto-plastic range as well as before the rupture-during the formation of the neck. It can be observed that the weld and HAZ has a significantly lower strain compared to the base material.

Distribution of strain ϵ_y along the length of tensed sample (55 mm in both direction from the center point of the sample) is illustrated in Fig. 4. Strain distribution is shown in the central axis y for the base material and welded joint at different times. Visible decrease of strain is present in the joint where HAZ is present. The slight increase of strain in the weld can be because of the inaccurate selection of an additional material in GMAW method.

The comparison of strain ϵ_y at time $t=24$ s is presented in Fig. 4c. It can be observed that for the base material higher values of strain ϵ_y are present in comparison to welded joint.

Conclusions

The use of multi-camera 3D correlation system allowed the analysis of strain and deformation for the selected material points, lines or plane throughout

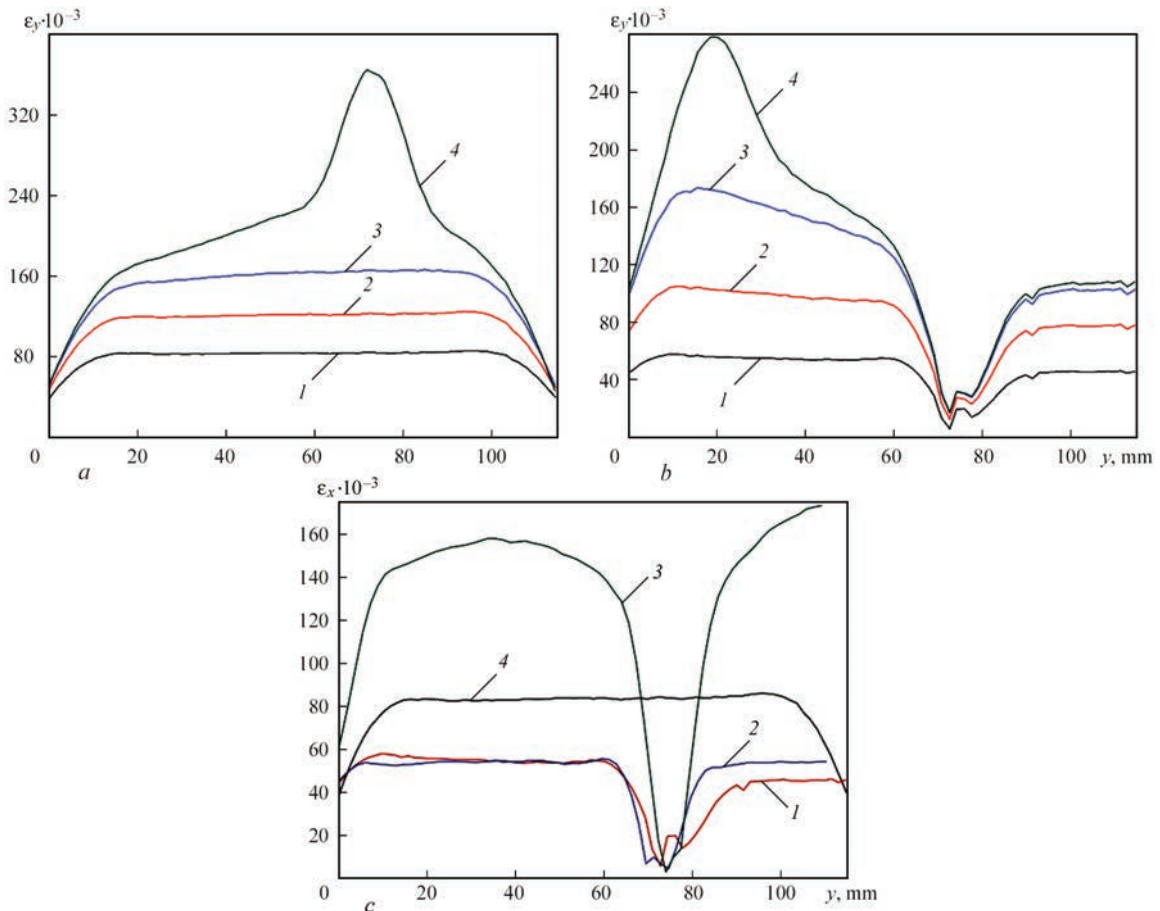


Fig. 4. Distribution of strain ϵ_y in the central axis y of sample for different times of tension: a — the base material; b — welded joint; c — comparison for time $t=24$ s (for a, b: 1 — 24s, 2 — 28, 3 — 32, 4 — 39; for c: 1-3 — welded joint 1-3; 4 — base material)

the measuring sample. Use of the system allowed the analysis of deformation and strain distributions in the weld and heat affected zone during tension test. It can be observed that lower strains occur in heat affected zone in comparison to the base material which in reference to pictures of microstructure confirm partial hardening of this zone. Visible increase of strain ϵ_y in the weld may be due to the inaccurate selection of an additional material in GMAW method. Obtained results allowed for a thorough analysis of mechanical properties separate zones of the joint and do not limit the tensile test to determine the global strength and plastic properties of welded material. Obtained experimental results may be very helpful in verifying mathematical and numerical models of thermomechanical phenomena occurring in welding processes.

References

1. Patorski K. (2005) *Interferometria laserowa*, Oficyna wydawnicza politechniki Warszawskiej.
2. C. Herbst, K. Splitthof. Basic of 3D Digital Image Correlation, Ulm, Dantec Dynamics GmbH.
3. Chu T.C., Ranson W.F., Sutton M.A, Peters W.H. (1985) Application of digital-image-correlation techniques to experimental mechanics. *Experimental Mechanics*, 25(3), 232-244.
4. Gower M.R., Shaw R.M. (2010) Towards a planar cruciform specimen for biaxial characterization of polymer matrix composites. *Applied Mechanics and Materials*, 24-25, 115-120.
5. Lord J.D., Digital image correlation (DIC) (2009) *Modern stress and strain analysis. A state of the art guide to measurement techniques*, BSSM Technical Editors: J. Eaton Evans, J.M. Dulie-Barton, R.L. Burguete, 14-15.
6. Palanca M., Cristofolini L. *Validation and optimization of the parameters of acquisition and processing for analysis through digital image correlation*. University of Bologna.

Доманский Т., Пекарска В., Кубиак М.

Університет технологій в Ченстохові.
ул. Генерала Яна Дабровського 69,
42-201, Ченстохова, Польща
E-mail: domanski@imipkm.pcz.pl

ИССЛЕДОВАНИЕ СВОЙСТВ СВАРНЫХ СОЕДИНЕНИЙ ПРИ ПОМОЩИ СИСТЕМ ISTRA 4D КОМПАНИИ DANTEC

Рассмотрен характер смещения и поля деформации, которые были измерены на различных стадиях растяжения плоских образцов с целью сравнения влияния различных технологических параметров на механические свойства сварных соединений. Результаты измерений также сравниваются с результатами испытания на растяжение основного материала, позволяющие оценить влияние процесса сварки на изменения механических свойств испытанной стали. Представлены данные смещений и деформаций в плоских сварных образцах из стали S355, выполненных гибридной сваркой с использованием электрической дуги и лазерного пучка. Процесс сварки выполнялся Yb:YAG лазером и электрической дугой при дуговой сварке металлическим электродом в защитном

газе. В сварочных испытаниях использовалась лазерная головка D70 Trumpf максимальной мощностью до 12 кВт и диаметром пятна лазерного пучка $d = 0,8$ мм. Сварные соединения были выполнены для различных технологических параметров процесса. Испытания на растяжение плоских образцов выполняли в соответствии с нормами PN-EN ISO 6891-1. Многокамерная корреляционная 3D система Dantec Q-400 ISTRA использована для измерения деформаций и смещений. Метод измерения основывается на корреляции цифровых изображений, записанных при помощи трех камер. Поверхность испытанных образцов покрывали слоем белой и черной краски. Измерение проводили посредством следащего перемещения за точками, которые покрывают поверхность образца, нагруженного продольным усилием. Библиогр. 6, рис. 4.

Ключевые слова: гибридная сварка, электрическая дуга, лазер, сварные соединения, механические свойства, испытания на растяжение, поля деформации

Доманський Т., Пекарська В., Кубіак М.

Університет технологій в Ченстохові.
вул. Генерала Яна Дабровські 69,
42-201, Ченстохова, Польща
E-mail: domanski@imipkm.pcz.pl

ДОСЛІДЖЕННЯ ВЛАСТИВОСТЕЙ ЗВАРНИХ З'ЄДНАНЬ ЗА ДОПОМОГОЮ СИСТЕМ ISTRA 4D КОМПАНІЇ DANTEC

Розглянуто характер зміщення і поля деформації, які були виміряні на різних стадіях розтягування плоских зразків з метою порівняння впливу різних технологічних параметрів на механічні властивості зварних з'єднань. Результати вимірювань також порівнюються з результатами випробування на розтягнення основного матеріалу, що дозволяють оцінити вплив процесу зварювання на зміни механічних властивостей випробуваної сталі. Представлені дані зсувів і деформацій в плоских зварних зразках зі сталі S355, виконаних гібридним зварюванням з використанням електричної дуги і лазерного пучка. Процес зварювання виконувався Yb:YAG лазером і електричною дугою при дуговому зварюванні металевим електродом в захисному газі. У зварювальних випробуваннях було розроблено лазерну голівку D70 Trumpf максимальною потужністю до 12 кВт і діаметром плями лазерного пучка $d = 0,8$ мм. Зварні з'єднання були виконані для різних технологічних параметрів процесу. Випробування на розтяг плоских зразків виконували відповідно до норм PN-EN ISO 6891-1. Багатокамерна кореляційна 3D система Dantec Q-400 ISTRA використана для вимірювання деформацій і зсувів. Метод вимірювання ґрунтується на кореляції цифрових зображень, записаних за допомогою трьох камер. Поверхні випробуваних зразків покривали шаром білої і чорної фарби. Вимірювання проводили за допомогою стеження за переміщенням точок, які покривають поверхню зразка, навантаженого поздовжнім зусиллям. Бібліогр. 6, рис. 4.

Ключові слова: гібридне зварювання, електрична дуга, лазер, зварні з'єднання, механічні властивості, випробування на розтягування, поля деформації

Поступила в редакцію 10.11.2017